

Nanosegregation in Na_2C_{60}

G. Klupp*, K. Kamarás*, N. M. Nemes[†], P. Matus*, D. Quintavalle**, L. F. Kiss*, É. Kováts*, S. Pekker* and A. Jánossy**

**Research Institute for Solid State Physics and Optics, Hungarian Academy of Sciences, P. O. Box 49, H-1525 Budapest, Hungary*

[†]*Instituto de Ciencia de Materiales de Madrid, Cantoblanco, 28049 Madrid, Spain*

***Department of Experimental Physics, Budapest University of Technology and Economics, Budafoki út 8, Budapest, Hungary H-1111*

Abstract.

There is continuous interest in the nature of alkali metal fullerides containing C_{60}^{4-} and C_{60}^{2-} , because these compounds are believed to be nonmagnetic Mott–Jahn–Teller insulators. This idea could be verified in the case of A_4C_{60} , but Na_2C_{60} is more controversial. By comparing the results of infrared spectroscopy and X-ray diffraction, we found that Na_2C_{60} is segregated into 3-10 nm large regions. The two main phases of the material are insulating C_{60} and metallic Na_3C_{60} . We found by neutron scattering that the diffusion of sodium ions becomes faster on heating. Above 470 K Na_2C_{60} is homogeneous and we show IR spectroscopic evidence of a Jahn–Teller distorted C_{60}^{2-} anion.

INTRODUCTION

The proposed [1] Mott–Jahn–Teller ground state of A_4C_{60} ($\text{A} = \text{K}, \text{Rb}, \text{Cs}$) fullerides was experimentally verified by EELS [2], NMR [3] and infrared (IR) [4] spectroscopies. Theory predicts a similar effect in fullerides with C_{60}^{2-} ions, the electron-hole inverted analogue of C_{60}^{4-} . Na_2C_{60} is the only known alkali-metal fulleride that is believed to contain the C_{60}^{2-} dianion and there were several attempts to verify the Mott–Jahn–Teller insulating ground state in this compound as well. Experimental results were not unambiguous [3], e.g. a very weak metallic behavior was found in Na_2C_{60} , but it was concluded that K_4C_{60} and Na_2C_{60} have essentially the same Mott–Jahn–Teller ground state.

In contrast, our infrared, X-ray and neutron scattering experiments indicate that Na_2C_{60} is not a good model system to investigate the ground state of A_2C_{60} fullerides. Above 470 K Na_2C_{60} is homogeneous and at high temperatures we find indication for Jahn–Teller distorted C_{60}^{2-} ions. The IR spectroscopy and X-ray diffraction results at ambient temperatures show, however, a nanosegregation of Na_2C_{60} into two phases.

EXPERIMENTAL

Na_2C_{60} was obtained by the reaction of stoichiometric amounts of Na and C_{60} at high temperature in a stainless steel capsule. The typical annealing sequence was first 23 days

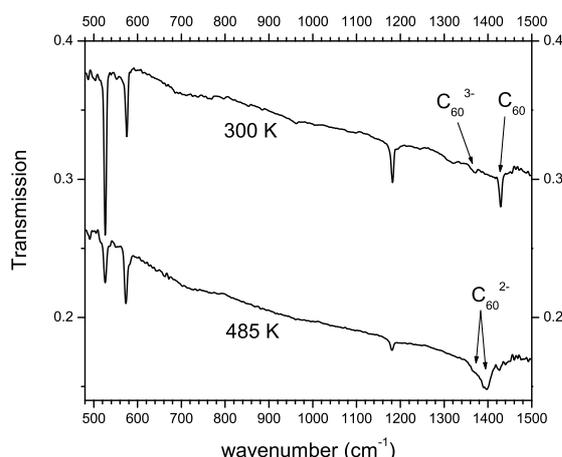


FIGURE 1. The IR spectra of Na₂C₆₀ at 300 K and at 485 K. At high temperature the absorption of the T_{1u}(4) mode could be fitted with two Lorentzians centered at the indicated positions, corresponding to C₆₀²⁻, while at 300 K lines corresponding to C₆₀ and C₆₀³⁻ appear.

at 350 °C and then 7 days at 450 °C. To homogenize the samples, we reground them about once every five days. Due to the air sensitivity of Na₂C₆₀, the reaction and the handling of the samples were carried out under inert atmosphere.

The sample was characterized by X-ray diffraction, which showed the material to be single phase *Pa* $\bar{3}$ (simple cubic) Na₂C₆₀. This result is identical to those in the literature [5].

Infrared measurements were performed on pressed KBr pellets in a Bruker IFS 28 FTIR instrument in a cryostat under dynamic vacuum. For neutron scattering measurements 1.2 g of Na₂C₆₀ powder was placed in an annular aluminum sample holder. Temperature dependent elastic fixed-window scans were taken on the High Flux Backscattering Spectrometer of the NIST Center for Neutron Scattering [6]. In this measurement, the incident neutron energy was fixed at 2.08 meV and scattering processes were detected near the elastic line within the 1 μ eV energy window of the resolution of the instrument[7]. Thus when a dynamic process became faster than the corresponding timescale of 0.8 ns, the measured intensity decreased.

RESULTS AND DISCUSSION

The charge state of C₆₀ anions can be evaluated from the quasilinear relationship between the charge state and the line position of the T_{1u}(4) IR mode [8]. We expect from this relation a line of C₆₀²⁻ at about 1380 cm⁻¹. Contrary to this expectation, there is no such line in the measured 300 K spectrum (Fig. 1) instead lines characteristic of neutral C₆₀ and of C₆₀³⁻ appear. In contrast to the narrow line of C₆₀, that of C₆₀³⁻ is smeared into a broad line. This kind of line broadening is common for A₃C₆₀ phases and is caused by metallic electrons. The metallic character of an aggregate as small as a few C₆₀³⁻ mole-

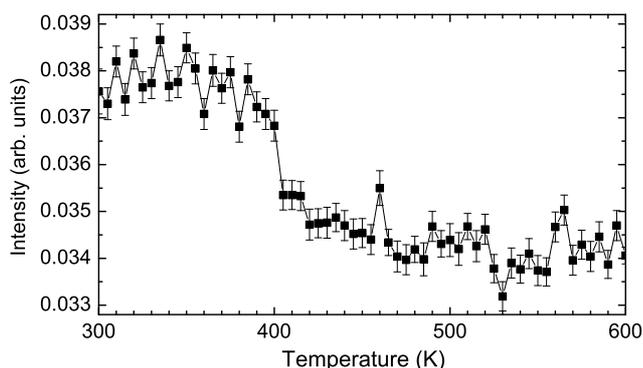


FIGURE 2. Elastic fixed window scan intensity of Na_2C_{60} at $Q = 1\text{\AA}^{-1}$.

cules is sufficient to broaden the IR line. Thus C_{60}^{3-} and C_{60} are not homogeneously distributed in the crystal lattice.

The observation of segregated Na_3C_{60} and C_{60} regions in the material by IR spectroscopy apparently contradicts the observation of a single phase by X-ray diffraction. However, if the size of segregated regions is smaller than about 10 nm, then X-ray diffraction cannot resolve the two phases but detects their average. Thus from the comparison of IR and X-ray diffraction measurements we conclude that Na_2C_{60} is nanosegregated at ambient temperatures.

The amount of neutral C_{60} in the material could be determined by its selective extraction with toluene. The concentration of the obtained C_{60} solution was measured with high-pressure liquid chromatography (HPLC). From this we could estimate the C_{60} content to be 26-33 % C_{60} in the nominally Na_2C_{60} material.

Heating the material to high temperatures proves that the stoichiometry of the sample is indeed Na_2C_{60} and that at high temperatures there is no neutral C_{60} left. The lines of neutral C_{60} disappear above 470 K, and a pair of lines appears at 1369 cm^{-1} and 1394 cm^{-1} (Fig. 1). This line pair is at about the expected frequency for the $T_{1u}(4)$ line of C_{60}^{2-} . Thus at room temperature the C_{60} content is not material left unreacted during the high temperature synthesis, but rather the product of the reaction $3\text{C}_{60}^{2-} \longrightarrow \text{C}_{60} + 2\text{C}_{60}^{3-}$ taking place on cooling after preparation. This reaction is reversible on heating and cooling, though a total retransformation at ambient temperature following treatment at high temperature is reached only after about two weeks.

The line pair of C_{60}^{2-} is the lower frequency analogue of the line pair of C_{60}^{4-} [4], indicating that C_{60}^{2-} is distorted to a D_{3d} or a D_{5d} geometry due to the molecular Jahn-Teller effect [4].

The synproportion reaction on heating ought to be accompanied by diffusion of Na ions in the lattice. This could be proven by neutron scattering. Figure 2 shows the temperature dependence of the elastic line at $Q = 1\text{\AA}^{-1}$. The intensity shows a Debye-Waller-type overall decrease, but has an unusual drop near 400 K. We interpret this with the increase of the jump diffusion of sodium ions between tetrahedral and off-centered octahedral sites. Above 400 K it becomes fast enough to be resolved by the

instrument and the incoherent scattering contribution of the sodium ions is removed from the fixed-window intensity. The different transition temperatures found in the IR and neutron measurements may be due to the different timescales.

CONCLUSION

We propose that Na_2C_{60} is nanosegregated at room temperature. The two main phases of Na_2C_{60} are insulating C_{60} and metallic Na_3C_{60} . The size of the homogeneous regions is about 3-10 nm. The segregation disappears on heating when the jump diffusion of sodium ions becomes faster. A similar segregated phase, the "intermediate phase" is known for KC_{60} [9]. In Na_2C_{60} at high temperatures, the sodium distribution is homogeneous and a Jahn–Teller distortion of C_{60}^{2-} ions is observed.

ACKNOWLEDGMENTS

This work was supported by OTKA grants T 034198, T 049338, T 046700 and T 043255. This work utilized facilities supported in part by the National Science Foundation under Agreement No. DMR-0086210. We acknowledge the support of the National Institute of Standards and Technology, U. S. Department of Commerce, in providing the neutron research facilities used in this work.

REFERENCES

1. Fabrizio, M., and Tosatti, E., *Phys. Rev. B*, **55**, 13465 (1997).
2. Knupfer, M., and Fink, J., *Phys. Rev. Lett.*, **79**, 2714 (1997).
3. Brouet, V., Alloul, H., Garaj, S., and Forró, L., *Phys. Rev. B*, **66**, 155122 (2002).
4. Kamarás, K., Klupp, G., Tanner, D. B., Hebard, A. F., Nemes, N. M., and Fischer, J. E., *Phys. Rev. B*, **65**, 052103 (2002).
5. Yildirim, T., Hong, S., Harris, A. B., and Mele, E. J., *Phys. Rev. B*, **48**, 12262 (1993).
6. Meyer, A., Dimeo, R. M., Gehring, P. M., and Neumann, D. A., *Rev. Sci. Instrum.*, **74**, 2759 (2003).
7. Becker, T., and Smith, J. C., *Phys. Rev. E*, **67**, 021904 (2003).
8. Pichler, T., Winkler, R., and Kuzmany, H., *Phys. Rev. B*, **49**, 15879 (1994).
9. Faigel, G., Bortel, G., Tegze, M., Gránágy, L., Pekker, S., Oszlányi, G., Chauvet, O., Baumgartner, G., Forro, L., Stephens, P. W., Mihály, G., and Jánossy, A., *Phys. Rev. B*, **52**, 3199 (1995).